Nanoscale Carbon in Metals for Energy Applications

David R. Forrest[1], CAPT Lloyd Brown[2], Lourdes Salamanca-Riba[3], Jennifer Wolk[1], Peter Joyce[2] , Jie Zhang[1]

Nanotechnology for Energy, Healthcare and Industry
MS&T 2011, Columbus, OH
19 Oct 2011

[1] Naval Surface Warfare Center, Bethesda, MD
[2] U.S. Naval Academy, Annapolis, MD
[3] University of Maryland, College Park, MD

Report Documentation Page

Form Approved
OMB No. 0704-0188

1. REPORT DATE	2. REPORT TYPE	3. DATES COVERED
19 OCT 2011		**00-00-2011 to 00-00-2011**

4. TITLE AND SUBTITLE	5a. CONTRACT NUMBER
Nanoscale Carbon in Metals for Energy Applications	5b. GRANT NUMBER
	5c. PROGRAM ELEMENT NUMBER
6. AUTHOR(S)	5d. PROJECT NUMBER
	5e. TASK NUMBER
	5f. WORK UNIT NUMBER
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) **Naval Surface Warfare Center,Bethesda,MD,20817**	8. PERFORMING ORGANIZATION REPORT NUMBER
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)	10. SPONSOR/MONITOR'S ACRONYM(S)
	11. SPONSOR/MONITOR'S REPORT NUMBER(S)

12. DISTRIBUTION/AVAILABILITY STATEMENT
Approved for public release; distribution unlimited

13. SUPPLEMENTARY NOTES

14. ABSTRACT

15. SUBJECT TERMS

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT **unclassified**	b. ABSTRACT **unclassified**	c. THIS PAGE **unclassified**	**Same as Report (SAR)**	**27**	

Acknowledgements

- Azzam Mansour, XPS and XAS, NSWCCD
- Angela Whitfield, SEM of Cu, NSWCCD
- Jie Zhang, SEM of 6061, NSWCCD
- Al Brandemarte, metallography, NSWCCD
- Matt Hayden, tensile testing, NSWCCD
- Greg Archer, heat treatment, NSWCCD
- Kui Jin / Austin Baker, electrical resistivity, U. Maryland

➢ Jason Shugart, President, Third Millennium

➢ ONR Code 332, William Mullins

➢ NSWCCD Code 60 S&T Director, Dave Sudduth

Summary

- There is a new class of materials: Covetic
  - Third Millennium Metals, LLC; 12-yr development
  - “Immortal” nanocarbon phase, 50-200 nm, to 6 wt. % C
  - Well-dispersed, not graphite/diamond/fullerene
- Chemically bound to metal in a way we still need to understand; probably a new nano-effect
- Combination of analytic methods needed for C
- Nanoscale carbon raises the melting point
- Lower density
- Higher as-worked strength
- Higher thermal conductivity
- Higher electrical conductivity

Focus of Talk

- Background
- Form and distribution of carbon
- Analytical methods
- Properties
  - AA6061
  - Copper
- Applications

Background

- Third Millennium Metals, LLC
- Under development since 1999
- Conversion occurs in melt
  - Al, Cu, Au, Ag, Zn, Sn, Pb and Fe
  - Carbon powder → nanoscale C
- Stable after conversion
- Process development and scale up is ongoing
- Producing laboratory quantities now, 10-15 lb heats → 100-lb heat capacity soon

Examples of nanoscale effects between metals and C

Zhou, et al., “Copper Catalyzing Growth of Single-Walled Carbon Nanotubes on Substrates,” *Nano Letters 2006*, Vol. 6, No. 12, p. 2987-2990

Schaper, et al., “Copper nanoparticles encapsulated in multi-shell carbon cages,” *Applied Physics A: Materials Science & Processing*, v. 78, no. 1, p. 73-77 (2004).

Feng, et al., “Optical and structural studies of copper nanoparticles and microfibers produced by using carbon nanotube as templates,” (Proceedings Paper), Nanophotonic Materials III, Zeno Gaburro; Stefano Cabrini, Editors, Proceedings Vol. 6321, 30 August 2006.

E K Athanassiou , R N Grass and W J Stark, “Large-scale production of carbon-coated copper nanoparticles for sensor applications,” *Nanotechnology*, v. 17, no. 6, 28 March 2006.

E. A. Sutter and P. W. Sutter, “Giant Carbon Solubility in Au Nanoparticles,” *Journal of Materials Science*, v. 46, p. 7090-7097 (2011).

Distribution and Form of Carbon

SEM—Cu covetic, as-cast, 3.8% C

- 50-200 nm diameter particles
- Well-dispersed
- Remain intact upon remelting and resolidification

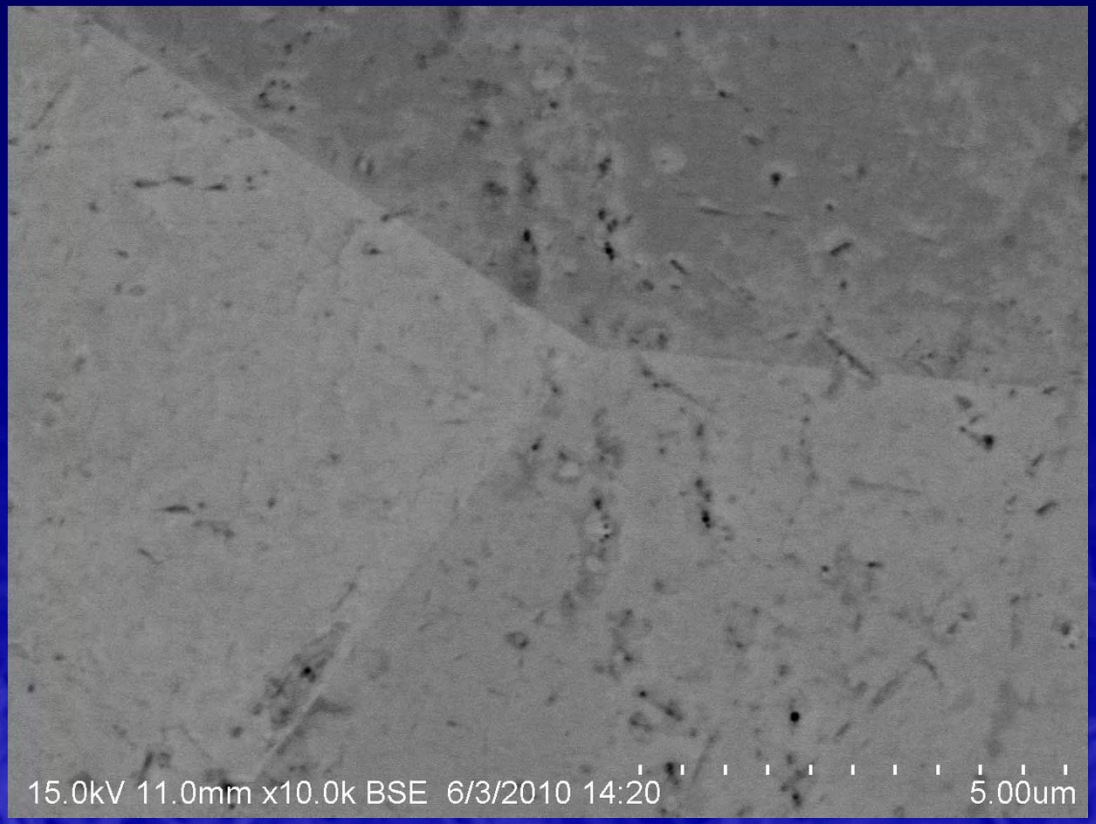

Metallographically as-polished surface

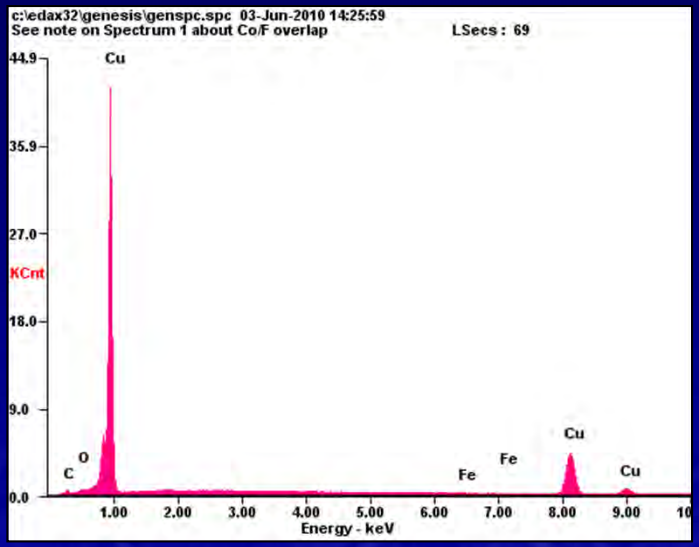

Element	*Wt %*	*At %*
C K	03.78	16.65
O K	01.29	04.25
FeK	00.32	00.30
CuK	94.61	78.79

SEM – AA6061 as-extruded, 2.7% nanoC

- 50-200 nm diameter particles
- Well-dispersed
- Remain intact upon remelting and resolidification
- Image analysis showed 1.1 – 2.6% C

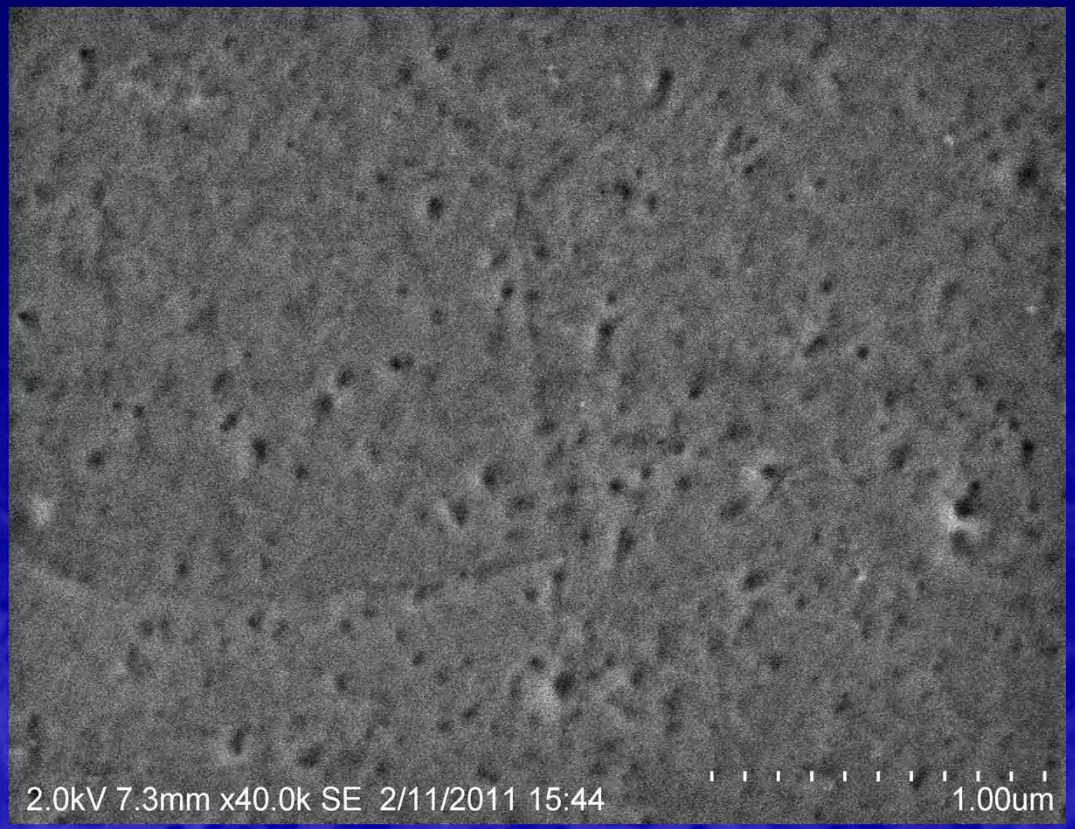

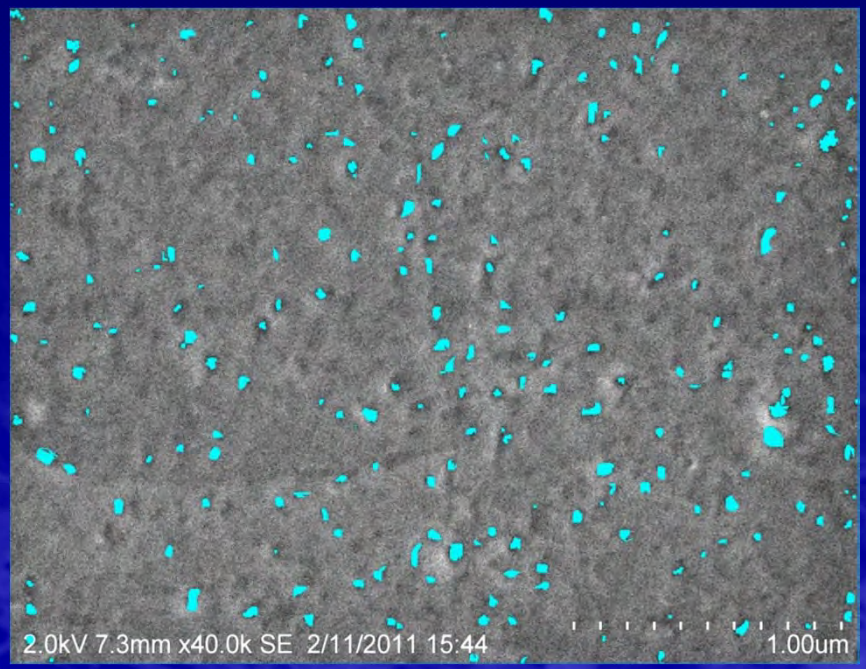

Metallographically polished surface

6061 as-extruded, 2.7% nanoC
Tensile fracture surface: ductile

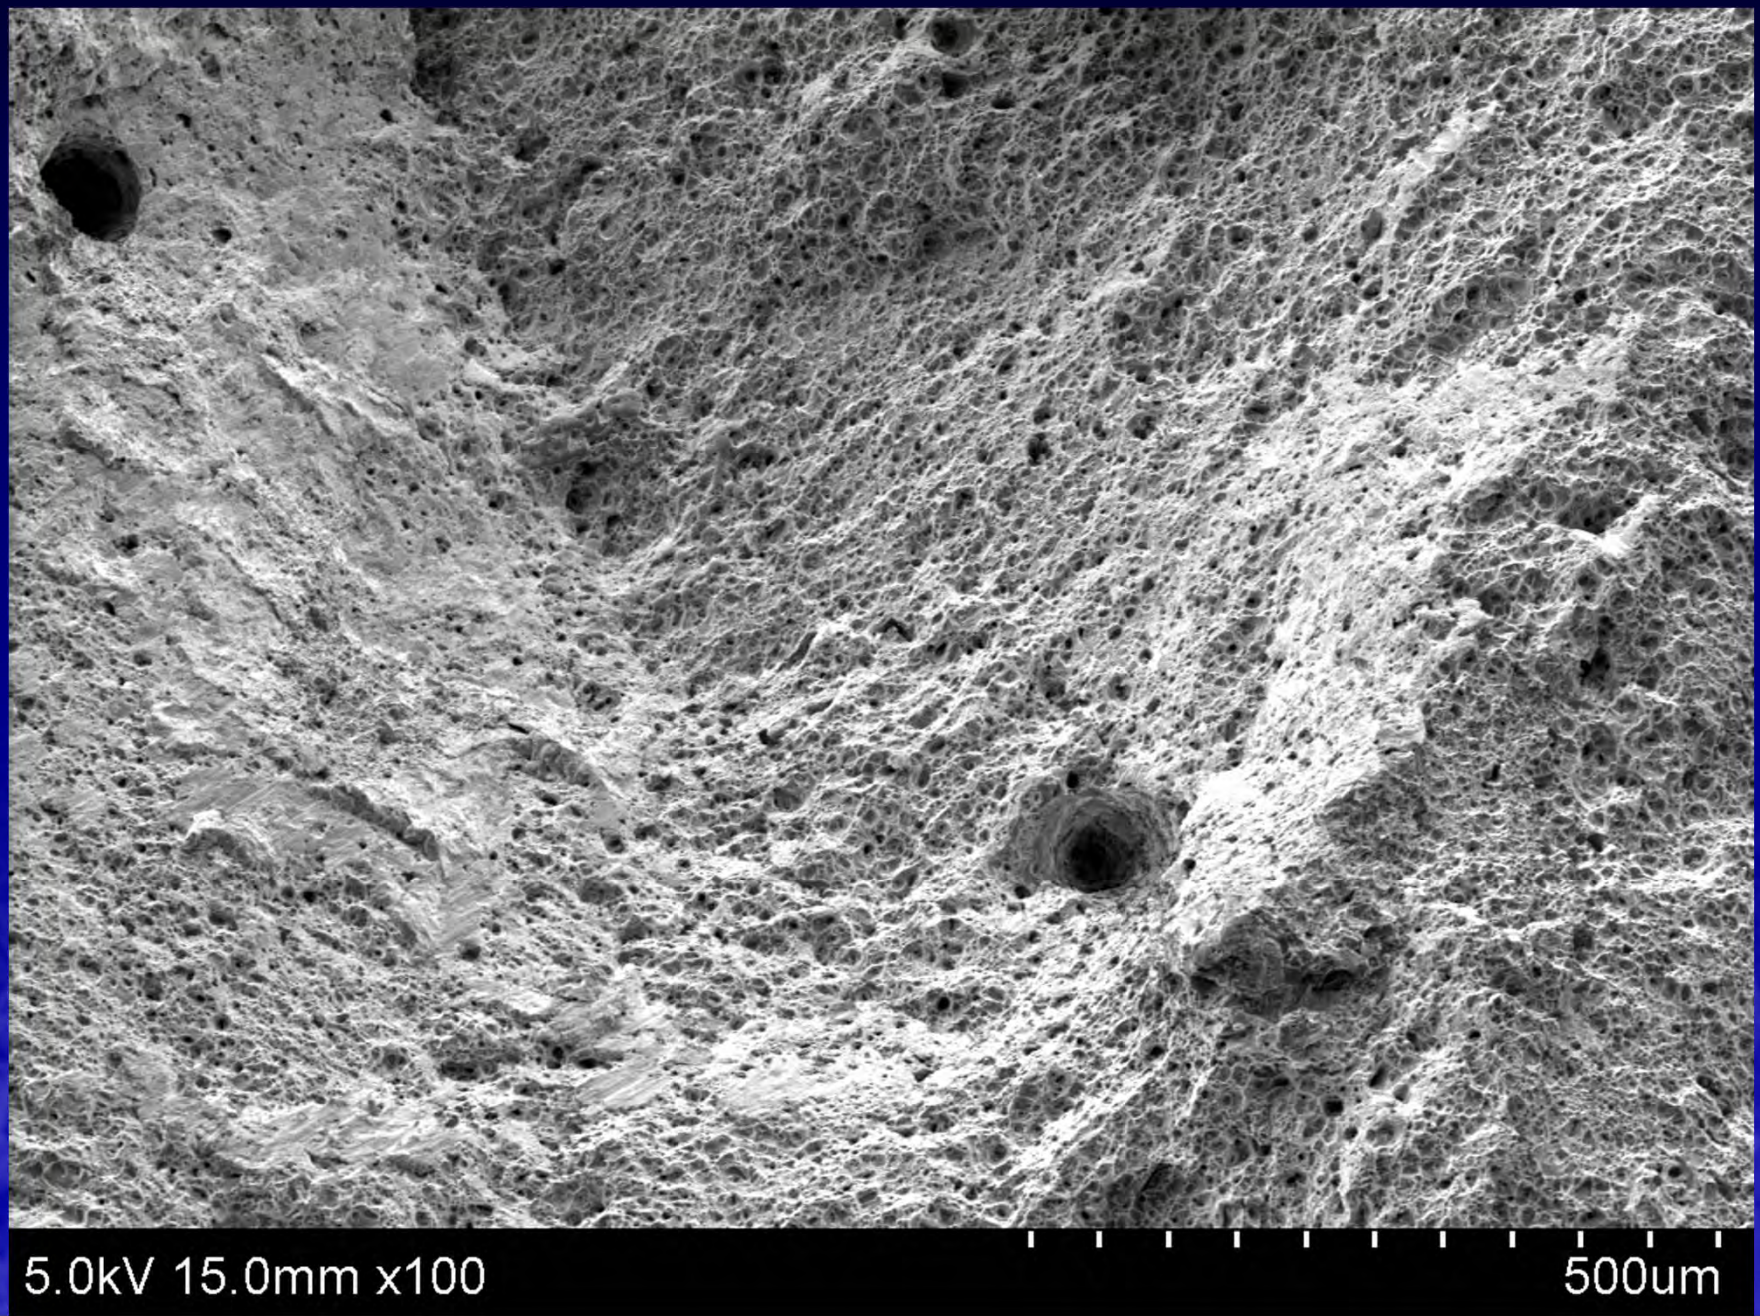

SEM – AA6061 as-extruded, 2.7% nanoC
Lourdes Salamanca-Riba

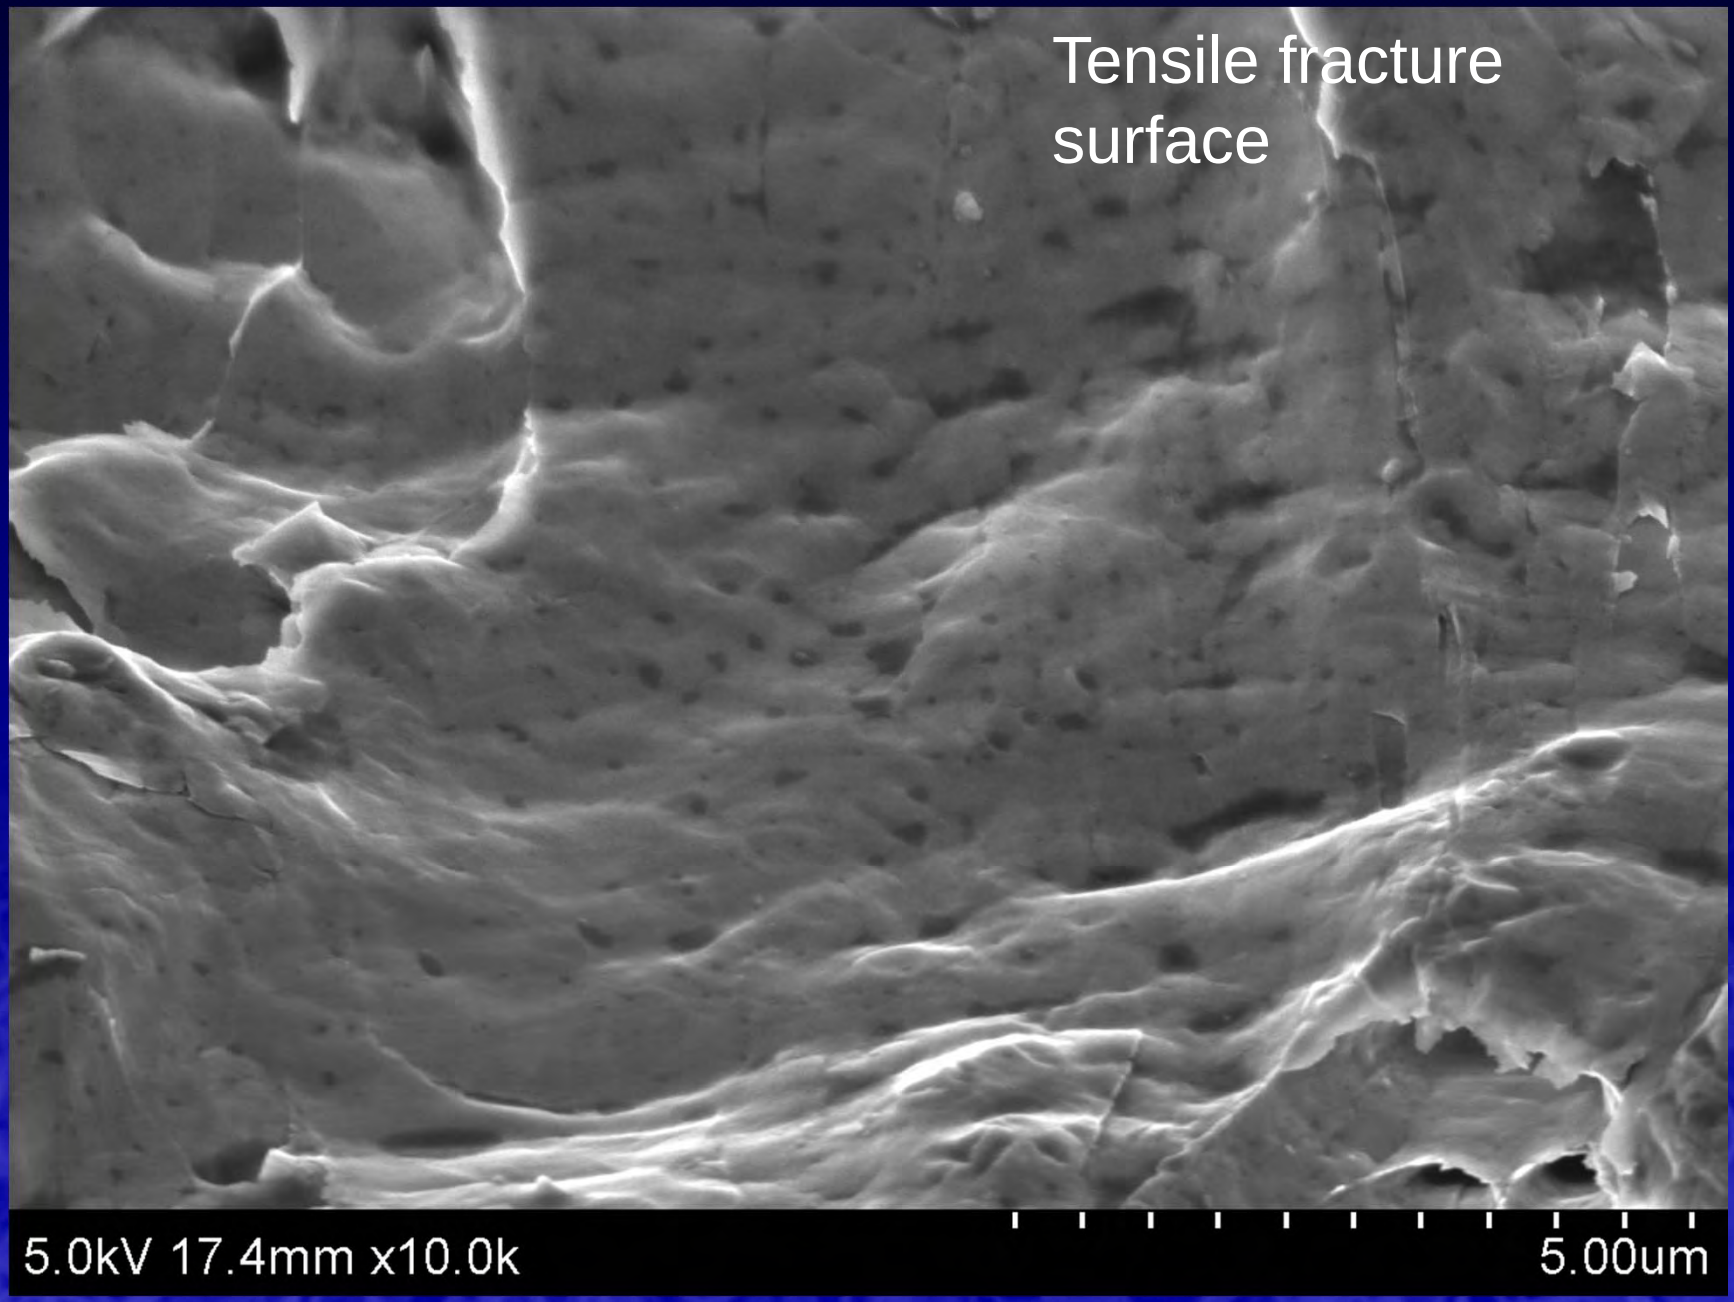

SEM – AA6061 as-extruded, 2.7% nanoC
Lourdes Salamanca-Riba

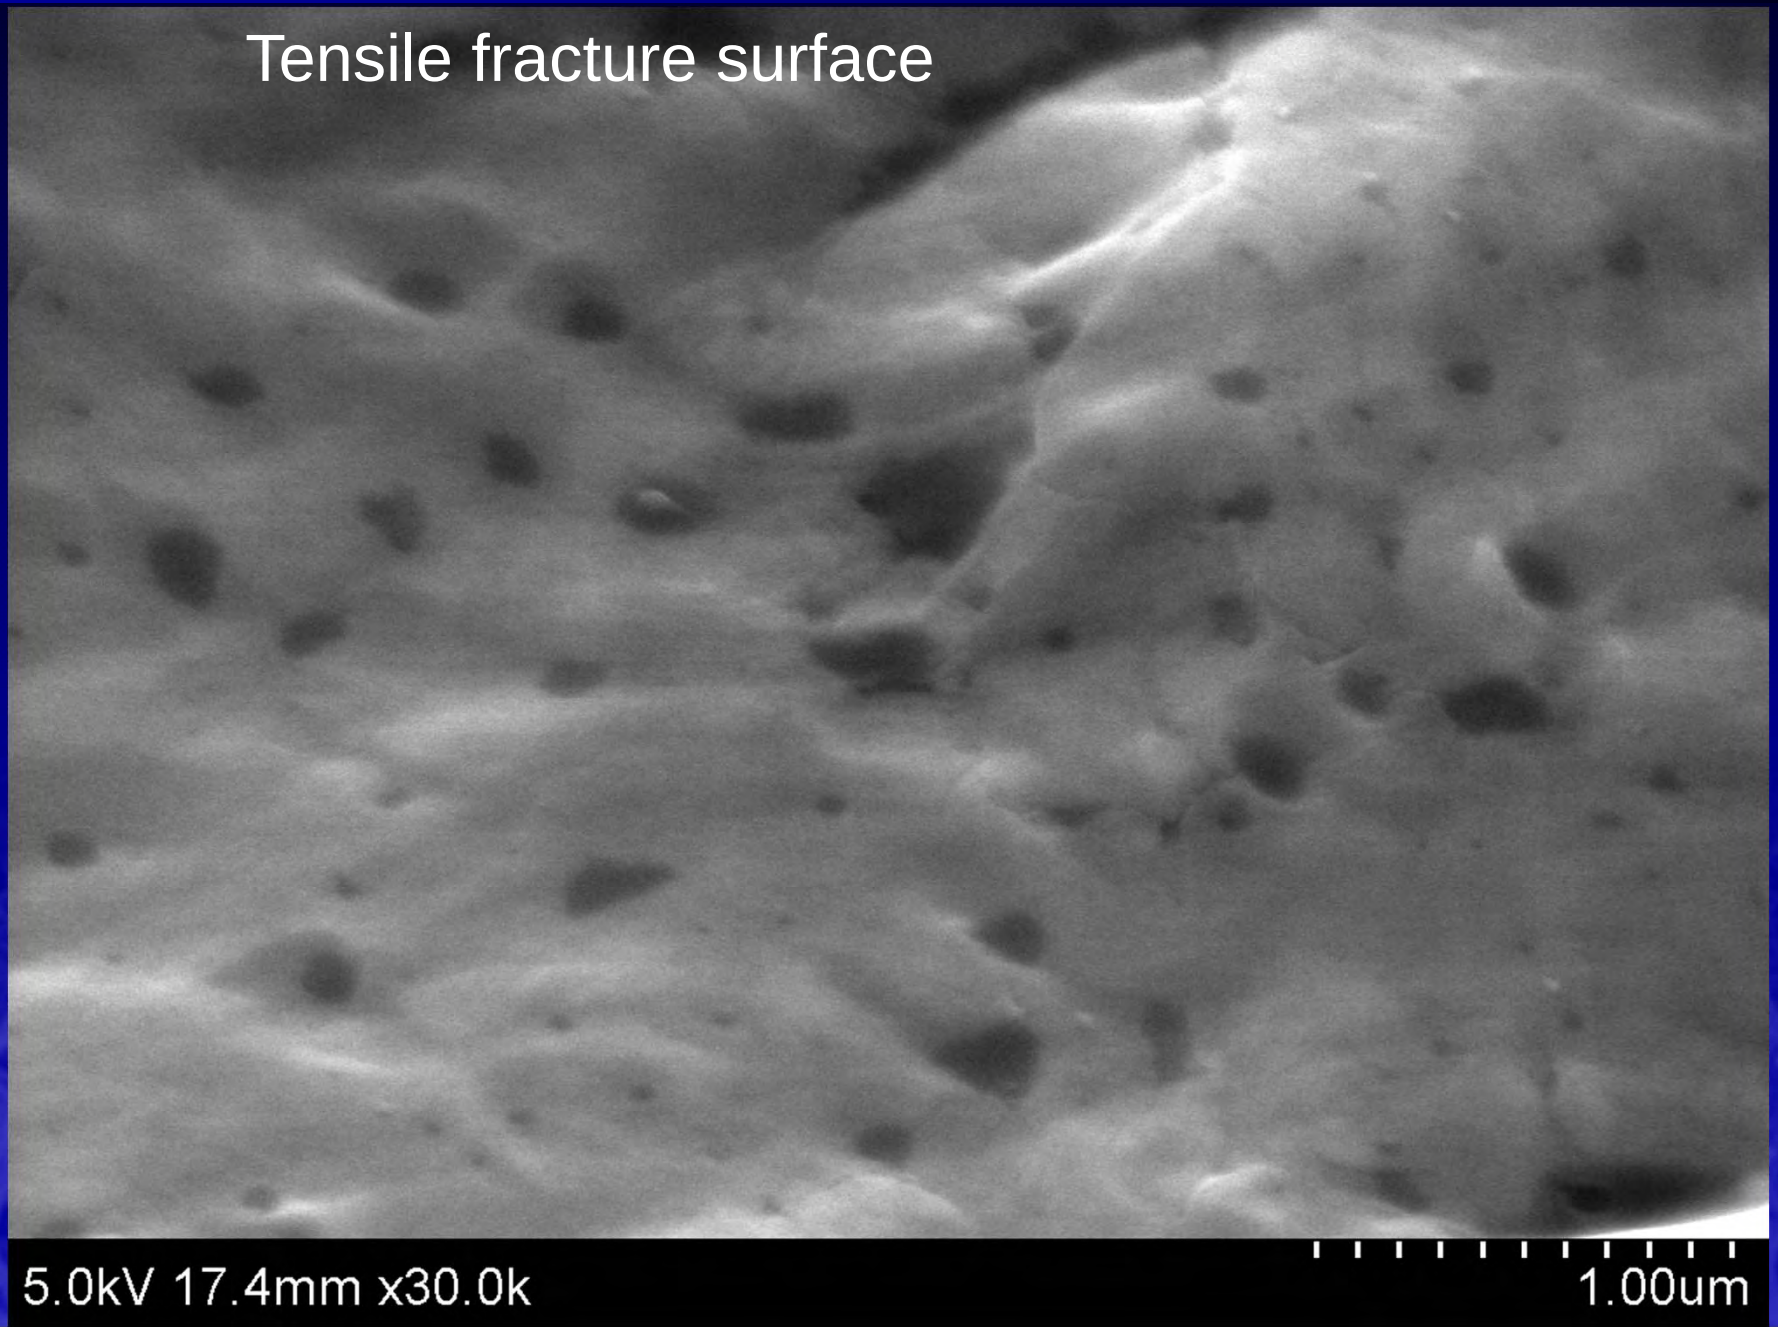

SEM – AA6061 as-extruded, 2.7% C

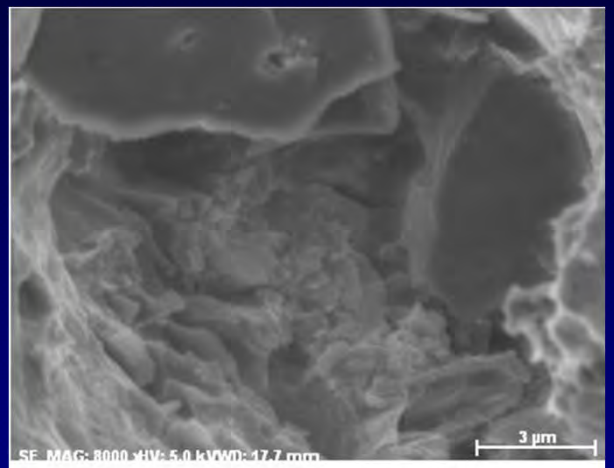

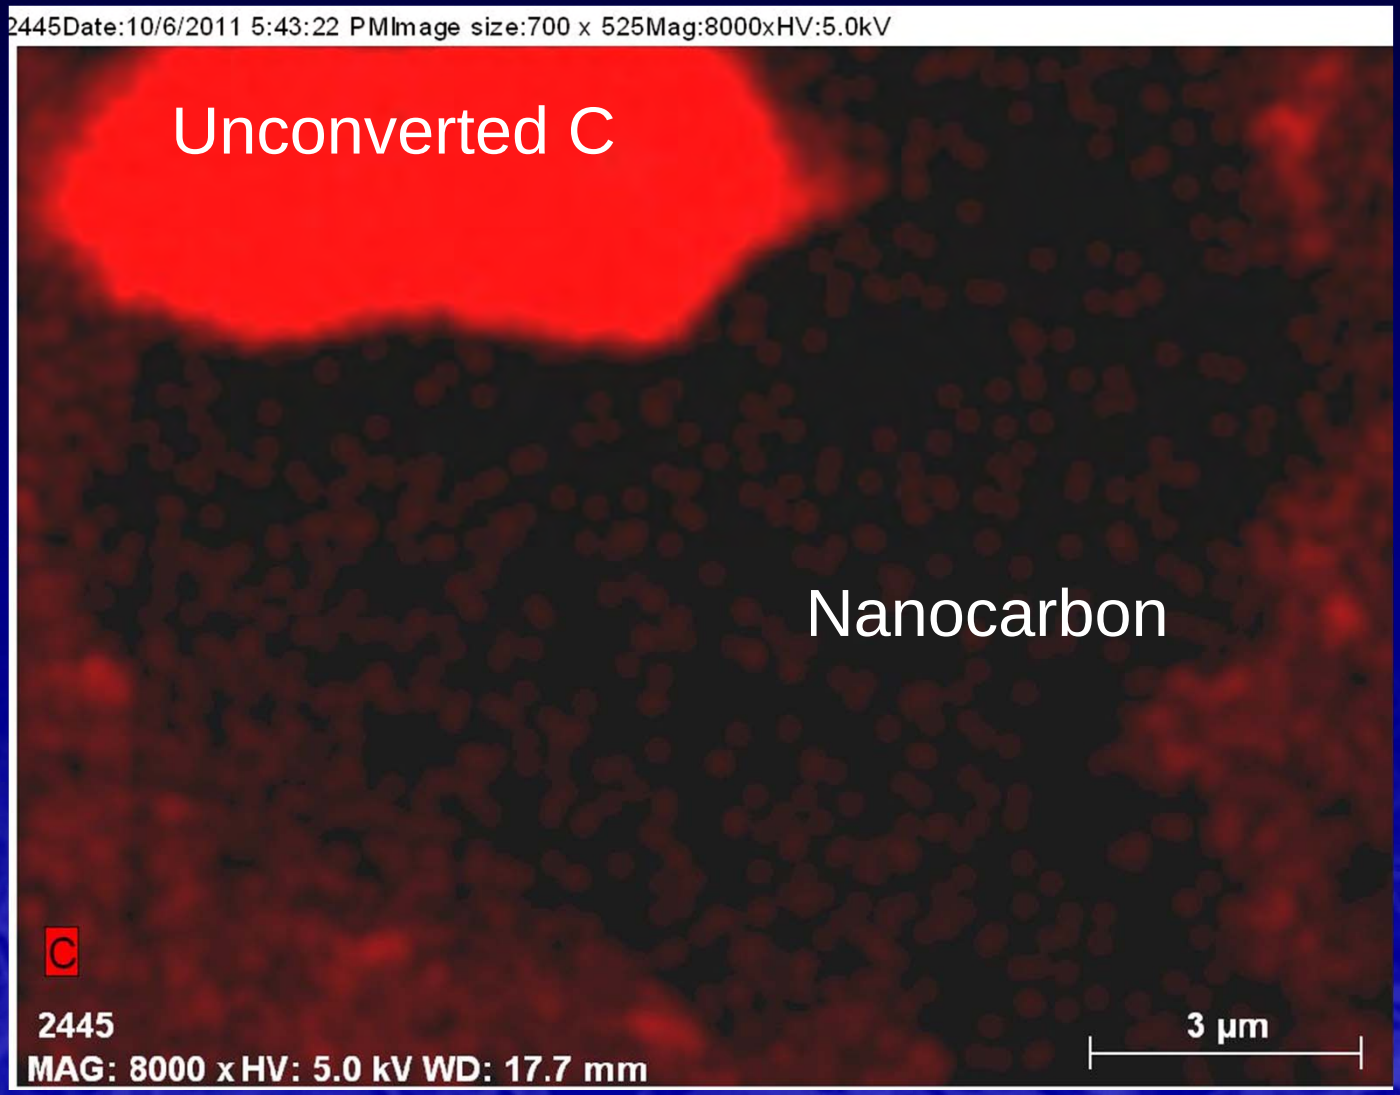

U. Maryland EELS Covetic Spectrum vs. Reference Spectrum of SWCNT

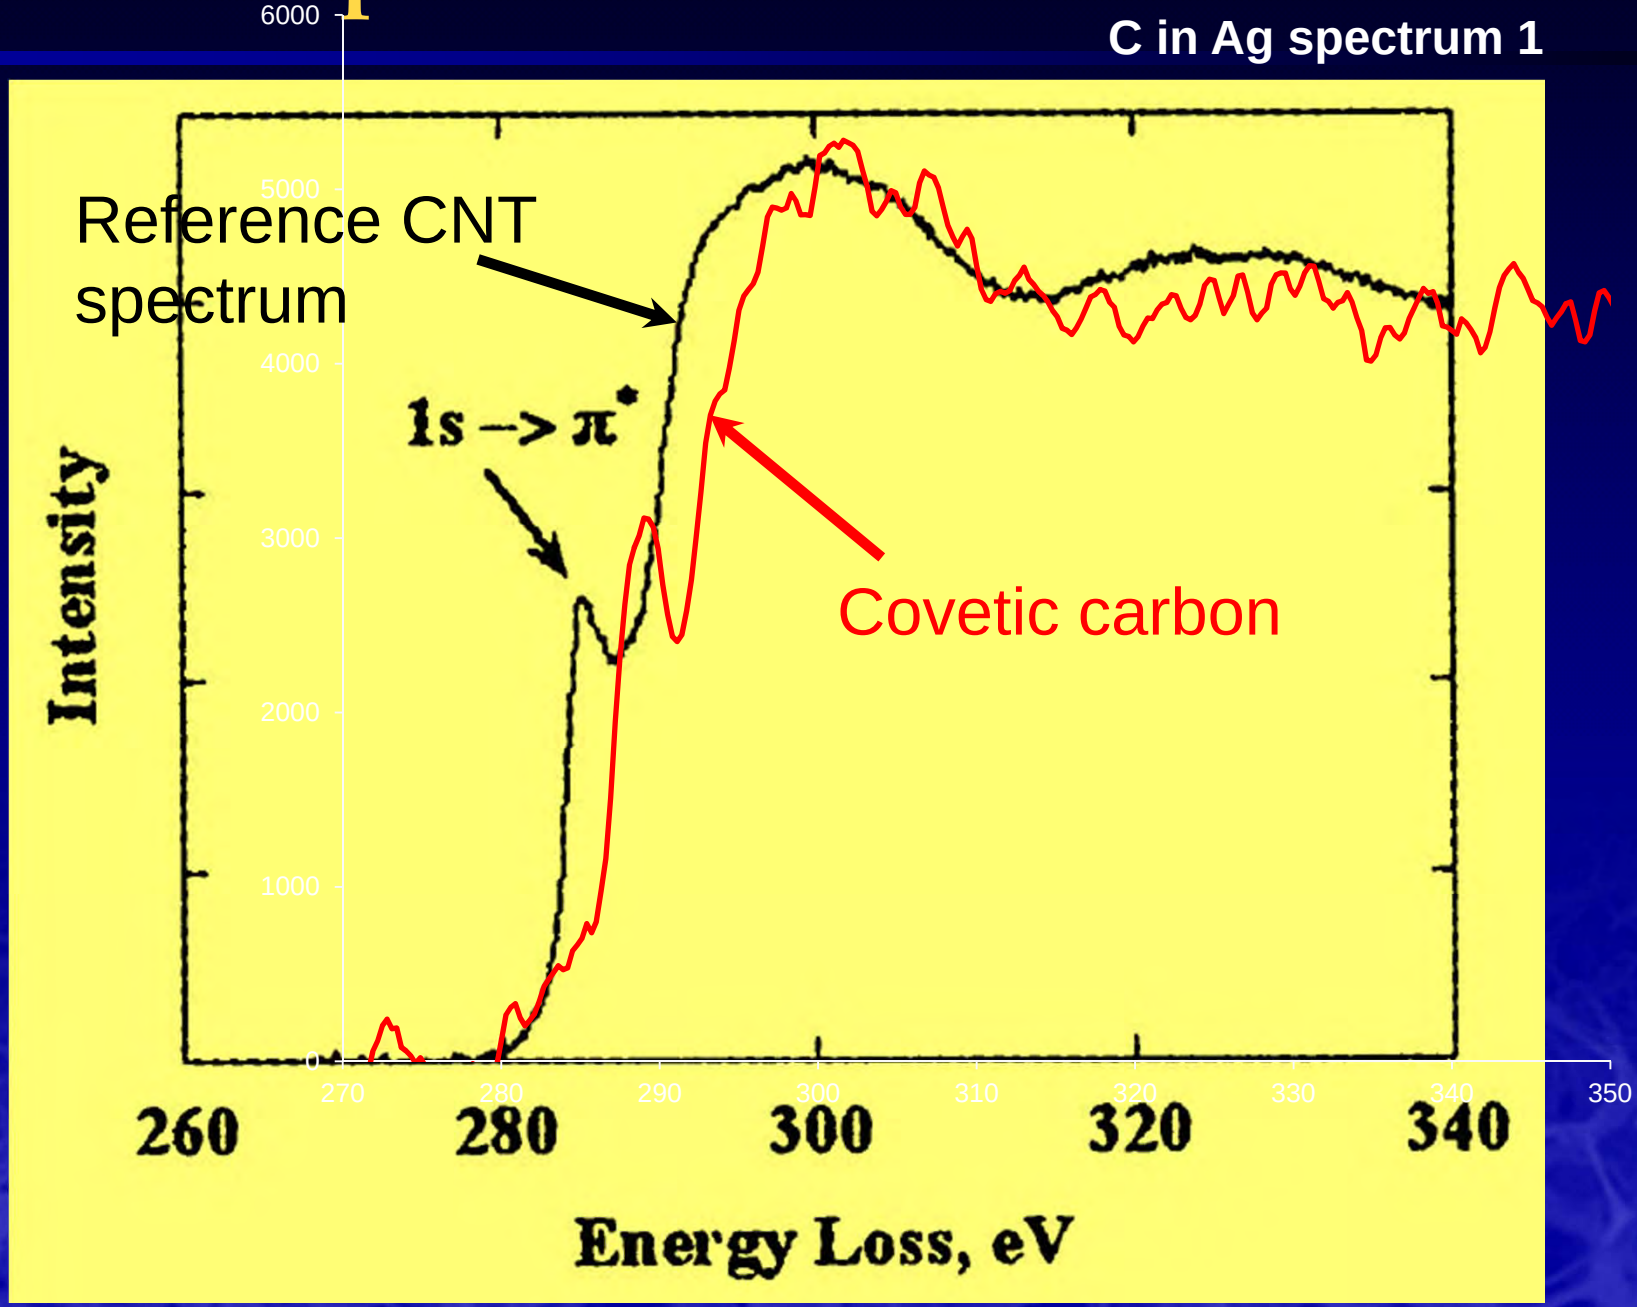

Schlittler, et al., "Single Crystals of Single-Walled Carbon Nanotubes Formed by Self-Assembly," Science, New Series, Vol. 292, No. 5519 (May 11, 2001), pp. 1136-1139

C Analysis in Cu Covetic

- Some techniques do not detect nanoscale C
- SEM-EDS and XPS best
- Standardization work needed

Method	Result (wt. %)
LECO	0.0016
DC-PES*	0.56
GDMS	0.0060
SEM-EDS	3.8
XPS (similar sample)	3.5
Density	< 4.3
% C reportedly added to the heat in the conversion process	5

* Direct Current Plasma Emission Spectroscopy ASTM E1097 to detect Cu

6061 Covetic (wt. %)

- Total carbon (3%) is detectable by EDS and XPS
- Unconverted carbon via LECO and GDMS
- LECO measurement: 0.300 wt. % C

	6061-0	H-49 Covetic	ASTM B211
C	0.003	0.300	0.05 max
Si	0.72	0.71	0.4 – 0.8
Fe	0.25	0.24	0.7 max
Cu	0.18	0.18	0.15 – 0.40
Mn	0.061	0.064	0.15 max
Mg	0.99	1.03	0.8 – 1.2
Cr	0.054	0.057	0.04 – 0.35
Zn	0.080	0.084	0.25 max
Ti	0.088	0.099	0.15 max
V	0.0072	0.0074	0.05 max

Mechanical and Thermophysical Properties

Increased melting point (DTA)

AA6061 solidus: 582°C → 619°C

Copper: 1085°C → 1105°C

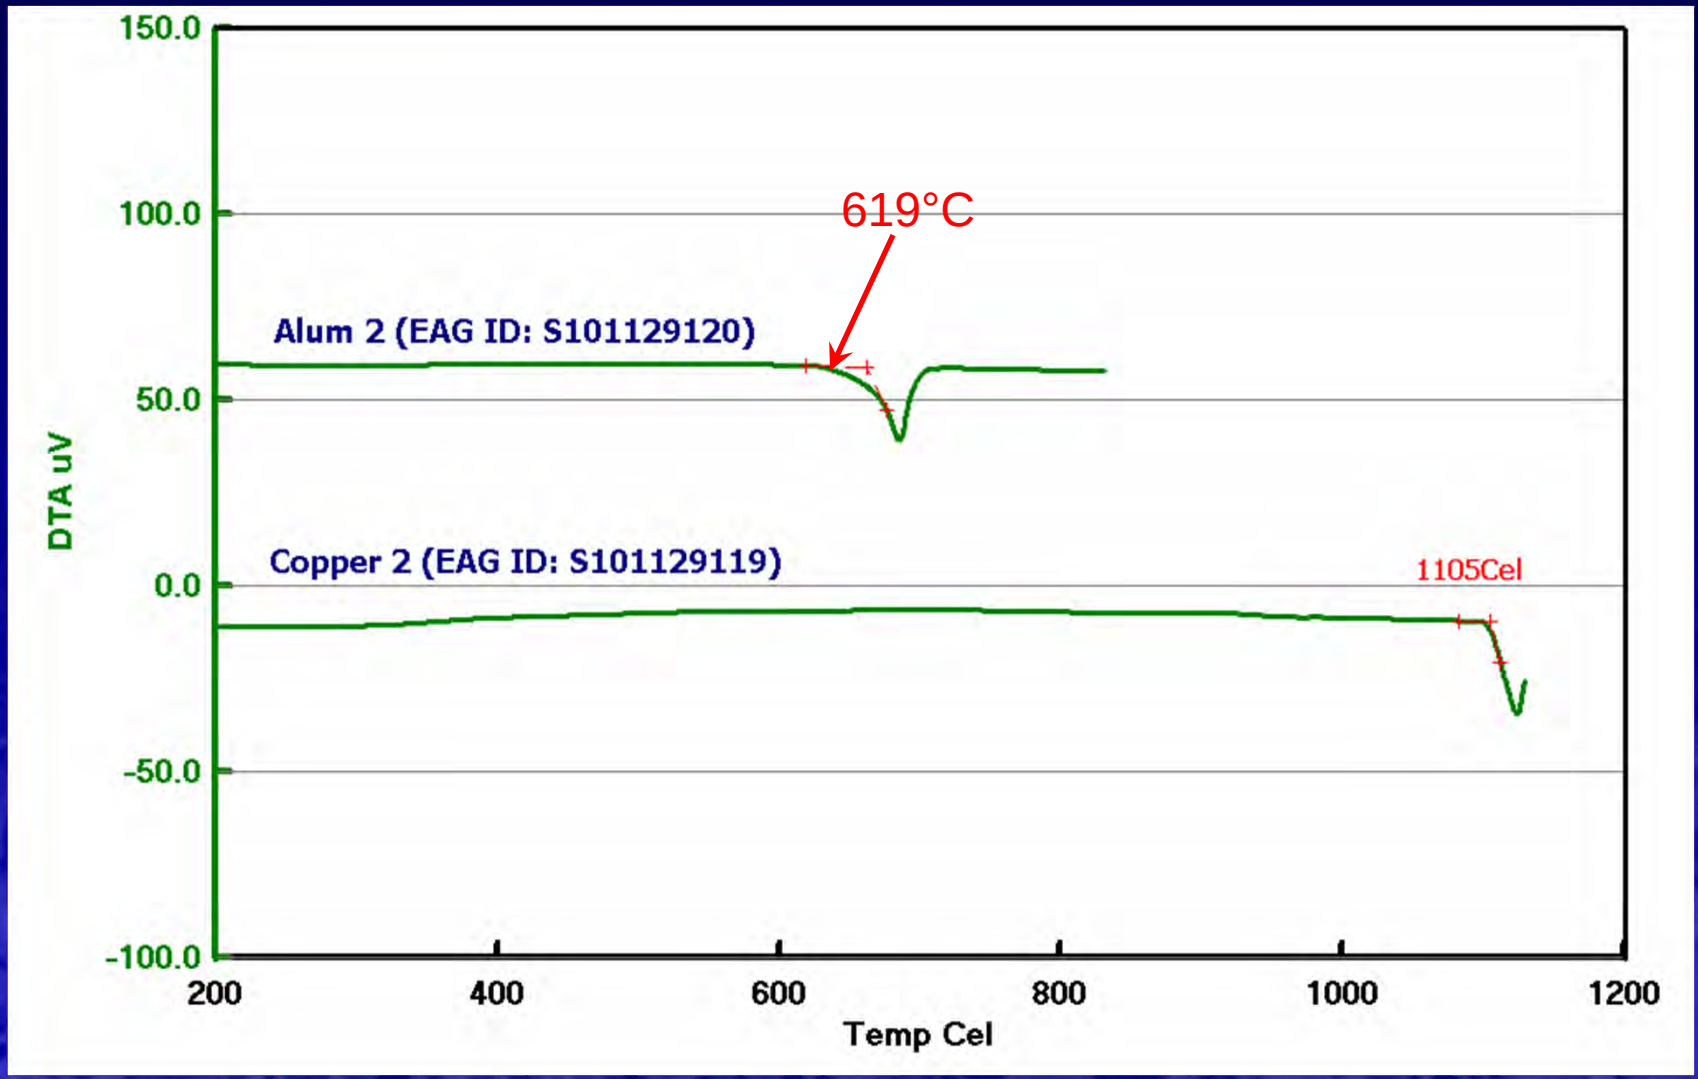

Density
Naval Academy, CDR Lloyd Brown

As-cast Cu Covetic

- Density = 7.92 g/cm^3 covetic
  8.94 g/cm^3 pure Cu
- Assuming ρ_{Cu} = 8.94 g/cm^3 and ρ_C = 2.25 g/cm^3, carbon content <= 4.33 wt%
- Roughly consistent with EDS measurement = 3.8%

Extruded 6061

- Density = 2.6729 g/cm^3 3% C
  2.6775 g/cm^3 0% C
- Assuming ρ_C = 2.25 g/cm^3, carbon content by density = 0.91 wt% vs 3

Covetic YS 30% higher as-extruded 400F

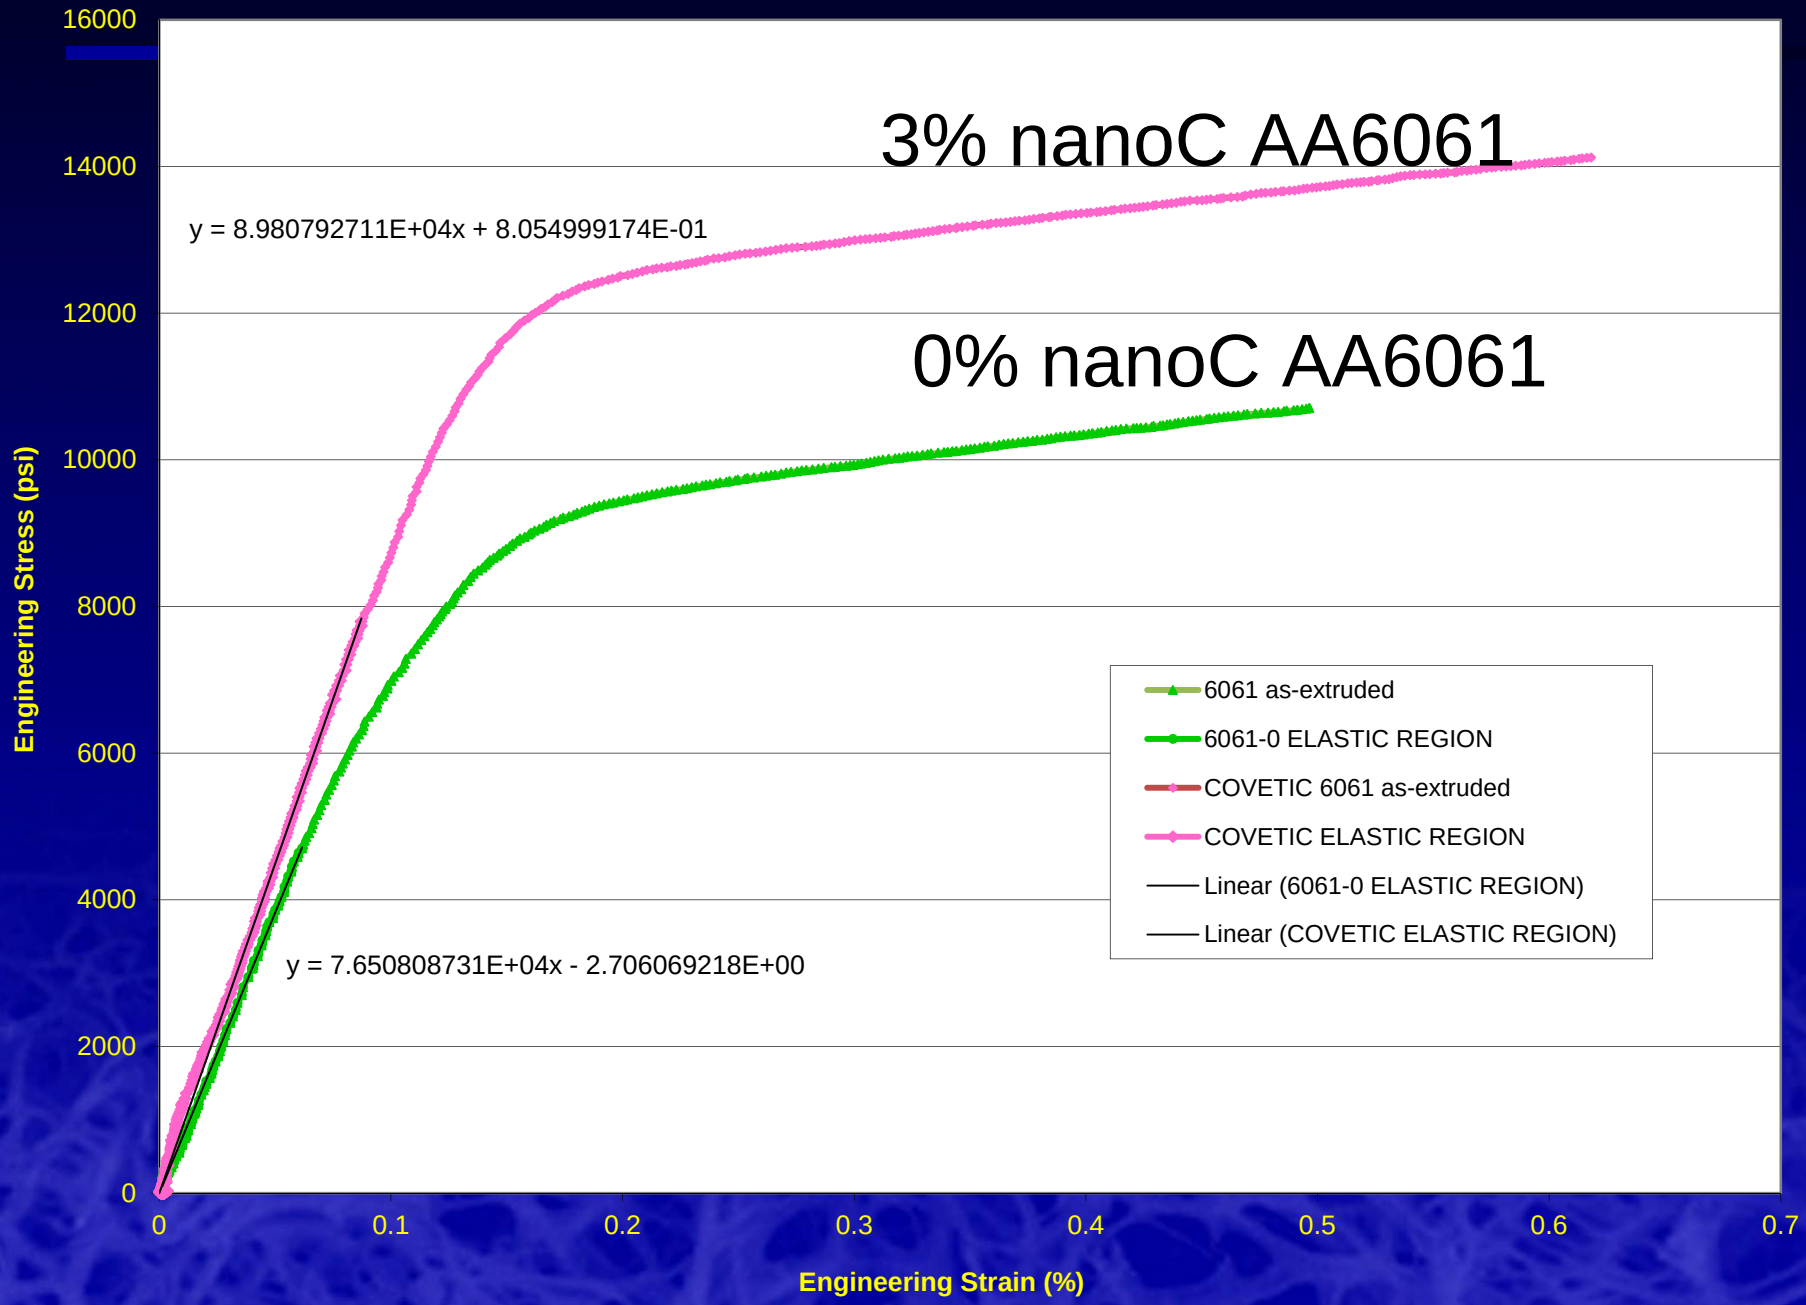

Tensile Curves:
No difference in T6 condition

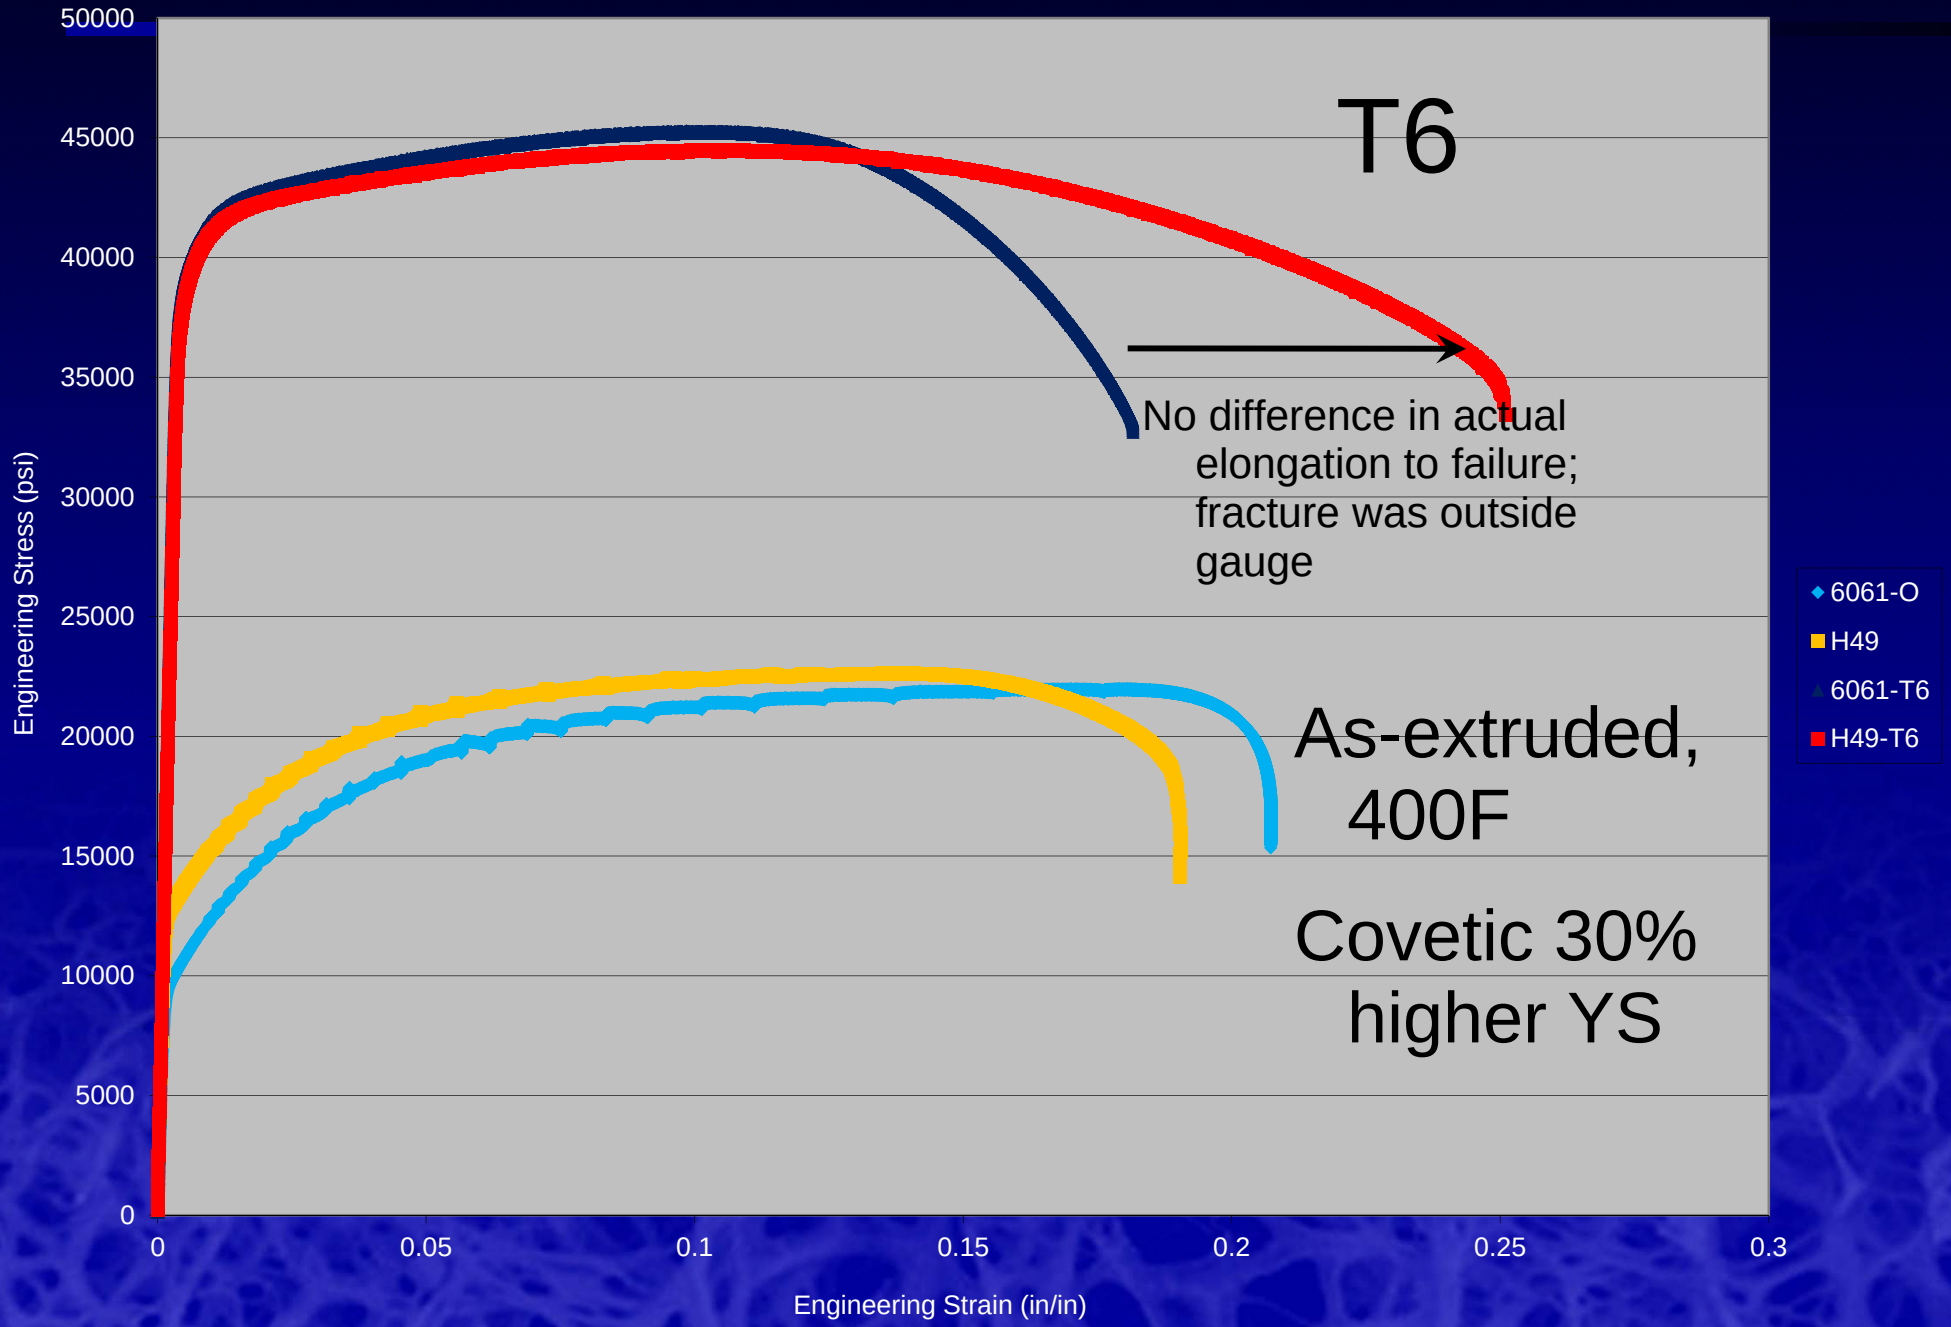

Electron Backscatter Diffraction (Wolk): Covetic resists grain coarsening

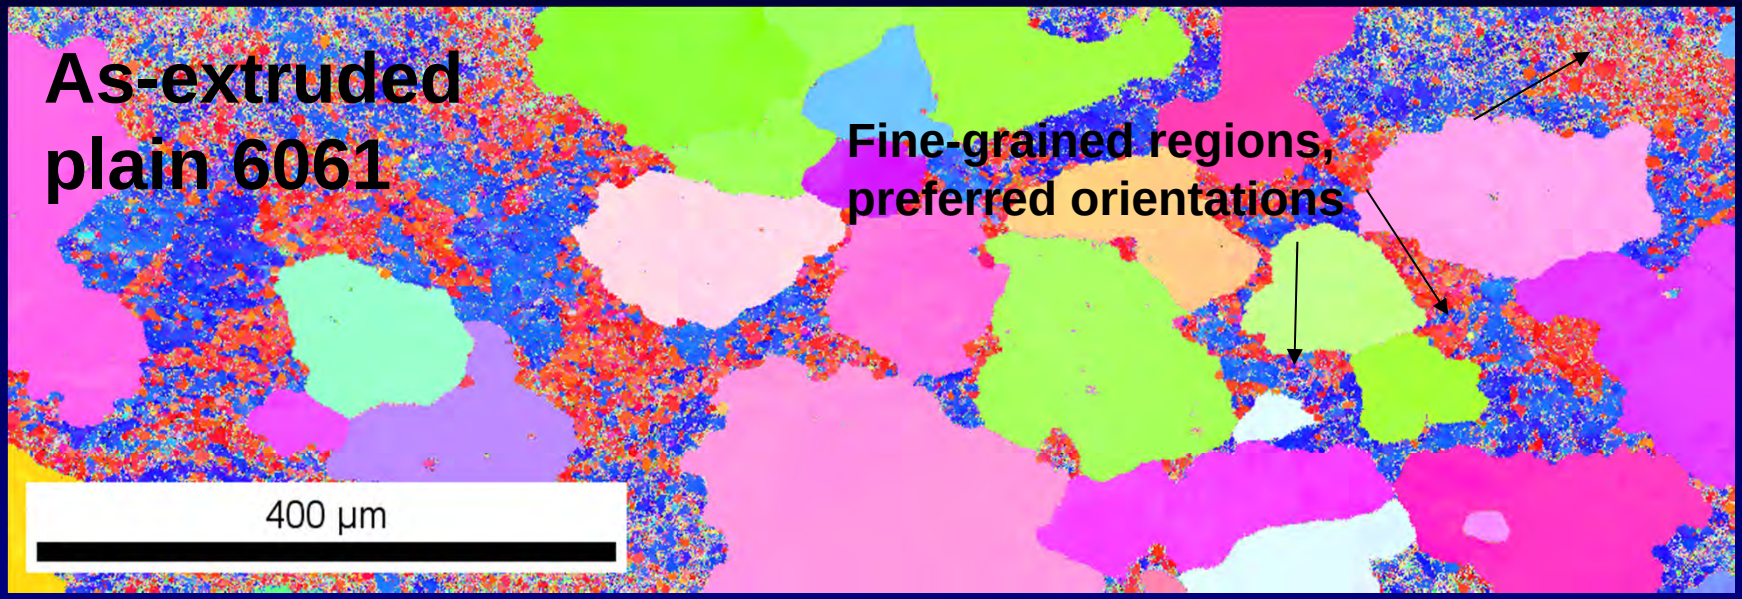



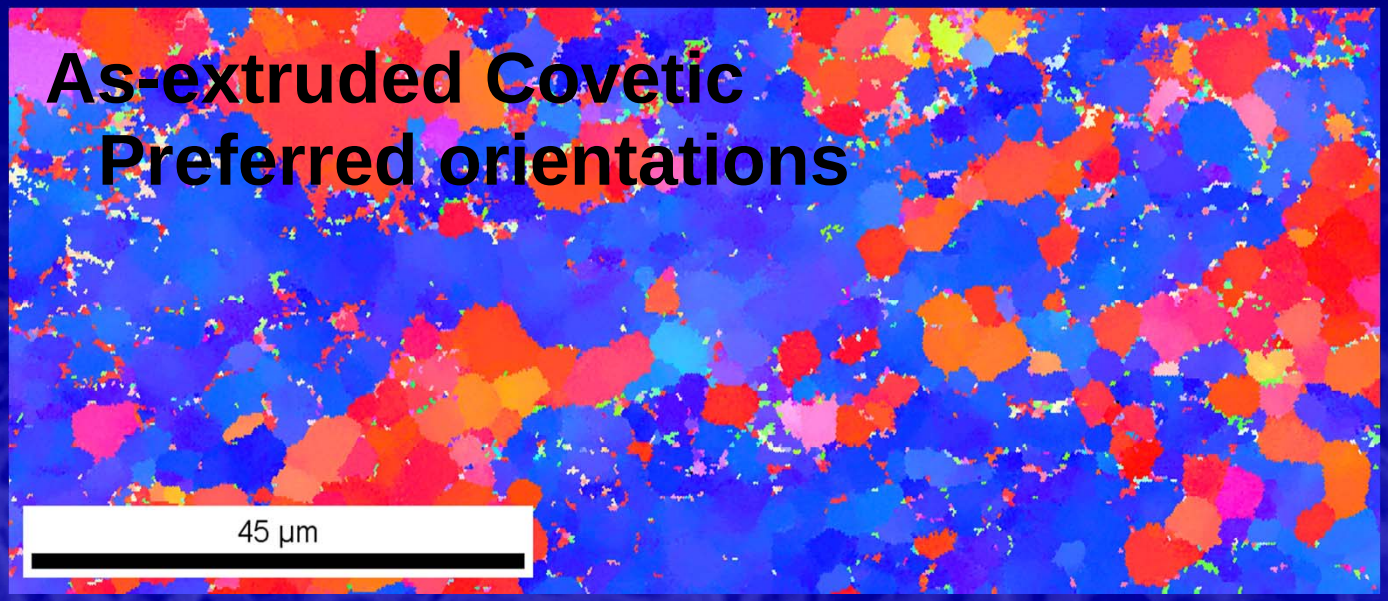

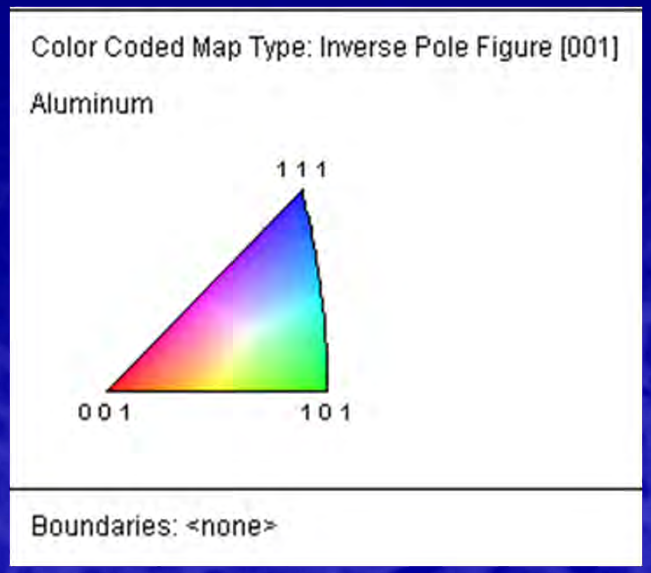

Electrical Conductivity, % IACS

0% C 6061	T6	47.4% Naval Academy
3% C 6061	T6	47.8% Naval Academy
3% C 6061	as-extruded	67.3% Naval Academy
"	"	54% U. Maryland
Electrical grade Al		61.8%

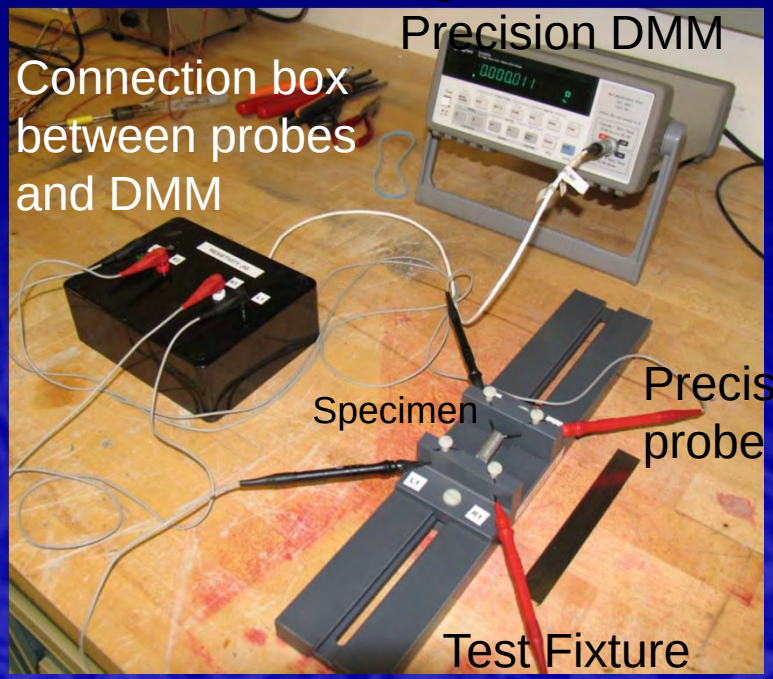

Anodic Polarization in Seawater

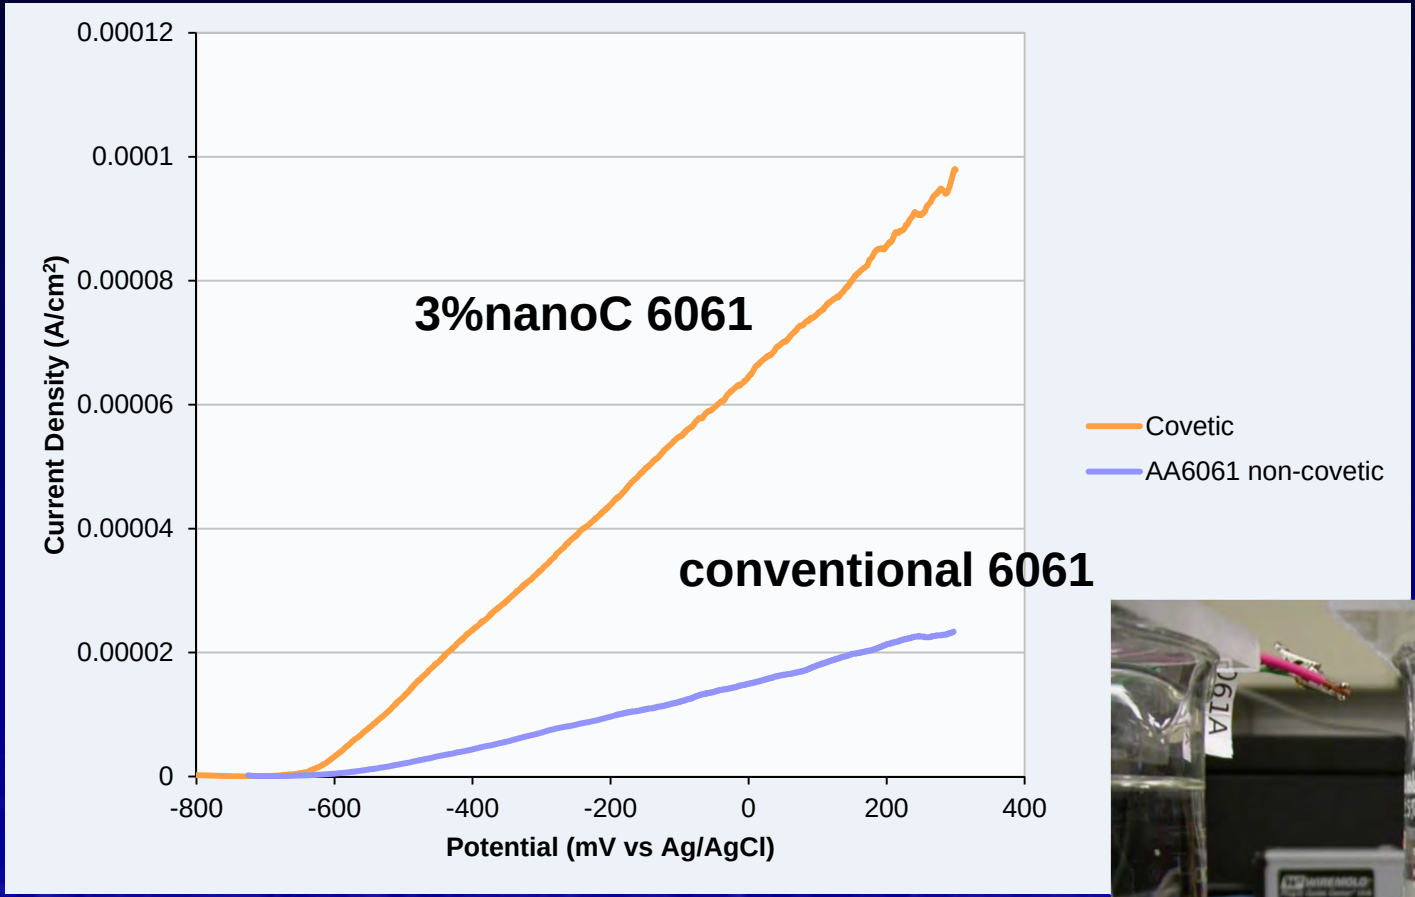

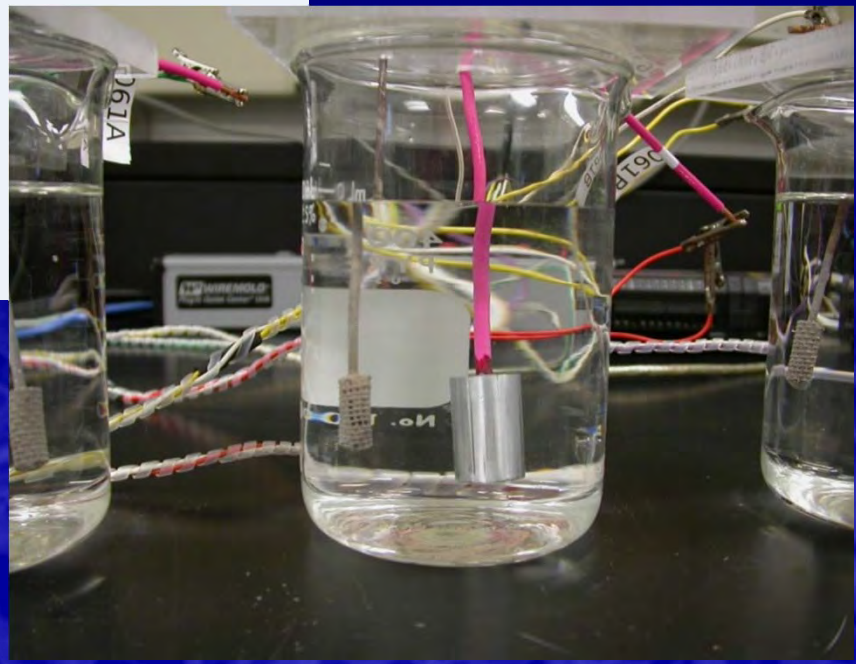

Factor of 5 increase in current in artificial seawater: Greater conductivity through the passive film?

Thermal conductivity

Khalid Lafdi (U. Dayton)

- Cold rolled copper
  - 0% nanoC 402 W/m-K
  - 3% nanoC 617 W/m-K in rolling direction
  - 3% nanoC 91 W/m-K orthogonal
- Normal 90Cu-10Ni: 71 W/m-K
  Covetic 90Cu-10Ni: 290 – 460 W/m-K

Energy Materials Testing Laboratory

- As-extruded Cu Covetic
  - 415 W/m-K in rolling direction vs. 402 annealed
  - 334 W/m-K orthogonal

Applications

- Lower density Cu with same electrical conductivity
  - Wiring, lightweight electrical motors
  - Ships, jets, helicopters, UAV's
- Anisotropic, high thermal conductivity Cu
  - Heat exchangers
  - Microelectronics
- High electrical conductivity aluminum
  - High tension lines
  - Electrodes and contacts

Summary

- There is a new class of materials: Covetic
  - Third Millennium Metals, LLC; 12-yr development
  - “Immortal” nanocarbon phase, 50-200 nm, to 6 wt. % C
  - Well-dispersed, not graphite/diamond/fullerene
- Chemically bound to metal in a way we still need to understand; probably a new nano-effect
- Combination of analytic methods needed for C
- Nanoscale carbon raises the melting point
- Lower density
- Higher as-worked strength
- Higher thermal conductivity
- Higher electrical conductivity